


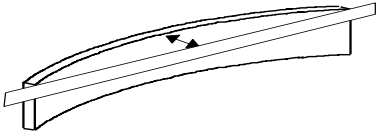
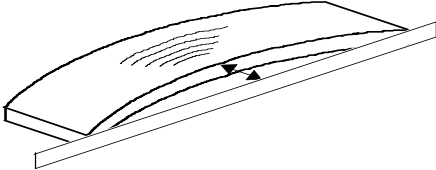
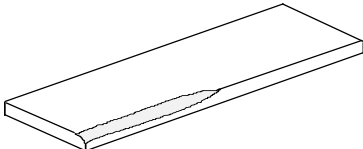
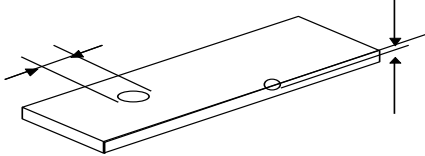
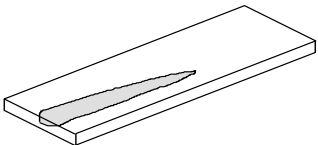
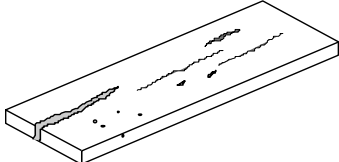


PUIDUKODA

WOOD FOR LIFE

**Rose GROUPE**
POUR MIEUX BÂTIR

Date: 15.06.2022	A+
Main profiles	Interior cladding and flooring
Slash (spike, splay) knots	Not permitted.
Sound (incl. black) knots	Max. 1/5 of the board width.
Unsound rotten knots	Not permitted on the visible side.
Bark-ringed knots	Not permitted on the visible side, less than 5 mm not considered.
Loose knots or knotholes	Not permitted on the visible side. Permitted on the edge provided no visible defect remains after joining two boards.
Max. permitted knots per meter	No restrictions.
Checks	Not permitted.
End splits	Max. permitted length ¼ of the board width, max. 10% of the volume, also through shakes.
Ring shakes	Not permitted.
Wane and mechanical damages	Not permitted.
Resin pockets	Max. length: 20 mm, max. 1 resin pocket per 1 meter, max. width not over 0.5 mm. Less than 10 mm not considered.
Bark pocket, scar	Not permitted.
Compression wood	Compression wood max. 10% of the volume.
Fungus infection (mould, blue stain, rot)	Not permitted.
Insect damage	Not permitted.
Moisture content	16 ± 2%. Special dry flooring 10 ± 2 %.
Surface quality	Hit & miss surface on the visible side not permitted.
Tolerance	Length: ± 10 mm, end matched boards ± 50 mm Thickness: ± 0,5 mm Width: ± 0,5 mm
	All the conditions are valid unless agreed otherwise. Max 5% deviation in quality grading allowed from total volume.

<p>Twist</p> 	<p>4 mm per worst 2 m, provided usage of the material is not restricted.</p>
<p>Bow</p> 	<p>10 mm per worst 2 m, provided usage of the material is not restricted.</p>
<p>Edge bow (crook)</p> 	<p>3 mm per worst 2 m, provided usage of the material is not restricted.</p>
<p>Wane</p> 	<p>Not permitted.</p>
<p>Knots</p> 	<p>See the previous page.</p>
<p>Discoloration (rot, fungus, blue stain)</p> 	<p>Rot, blue stain and fungus not permitted.</p>
<p>Checks and end shakes</p> 	<p>Checks and through fissures are not permitted. Max. permitted length of the end shakes $\frac{1}{4}$ of the board width, max. 10% of the volume, also through shakes.</p>